

## Supported Catalysts

**Heterotrimetallic RuMnMn Species on a Hydrotalcite Surface as Highly Efficient Heterogeneous Catalysts for Liquid-Phase Oxidation of Alcohols with Molecular Oxygen\*\***


Kohki Ebitani, Ken Motokura, Tomoo Mizugaki, and Kiyotomi Kaneda\*

The creation of a well-defined, active metal site on a solid surface not only opens up an avenue to materials that boost catalytic performance but also aids an understanding of the molecular basis of heterogeneous catalysis.<sup>[1]</sup> Modifying the coordination sphere of a metal species with other metals as ligands, which is a basic approach in organometallic and bioinorganic chemistry,<sup>[2]</sup> is also being applied to heterogeneous catalysis<sup>[3]</sup> because of the potential of performing unique catalytic reactions based on cooperation between diverse metals within a regular arrangement. In addition, this allows local compositional modeling for the strong metal–support interactions (SMSI) seen in supported metal catalysts.<sup>[4]</sup>

Hydrotalcite (HT), which is a layered, mixed hydroxide of Mg and Al,<sup>[5]</sup> has received attention as a material for advanced heterogeneous catalysts<sup>[6,7]</sup> because of the cation-exchange ability of the Brucite layer, the anion-exchange ability of the interlayer, its adjustable surface basicity, and adsorption capacity. Recently, we created a monomeric Ru<sup>IV</sup>-OH species on the HT (Ru/HT) surface by adsorption which turned out to be an excellent heterogeneous catalyst for the one-pot synthesis of  $\alpha$ -alkylated nitriles by a Ru-catalyzed alcohol oxidation coupled with a base-promoted aldol reaction.<sup>[7d]</sup> As part of our ongoing project on the functionalization of supported Ru catalysts to achieve environmentally friendly (“green”) organic syntheses, we present a novel HT-bound heterotrimetallic Ru<sup>IV</sup>Mn<sup>IV</sup>Mn<sup>IV</sup> species that has been structurally characterized on the atomic scale by X-ray absorption spectroscopy.<sup>[8]</sup> This material is an excellent solid catalyst for liquid-phase alcohol oxidation under mild conditions. This protocol to create a supported mixed-metal species can provide catalytically active compounds that are uniform in composition and distribution on a solid surface by applying concepts from coordination chemis-

try, and bridges the gap between homogeneous and heterogeneous catalysis.<sup>[9]</sup>

We obtained well-defined, heterotrimetallic RuMnMn species on the HT surface (RuMn<sub>2</sub>/HT) by immobilizing Mn cations onto Ru/HT. The Ru/HT was prepared by treating HT with an aqueous solution of RuCl<sub>3</sub>·*n*H<sub>2</sub>O.<sup>[7d]</sup> The retention of the HT interlayer distance (3.0 Å), as shown by XRD (X-ray diffraction),<sup>[10]</sup> indicated that both metal species are accommodated on the HT surface. The K-edge XANES (X-ray absorption near-edge structure) spectrum of the Ru and Mn of RuMn<sub>2</sub>/HT reveals that the surface Ru and Mn cations are in the oxidation state +IV. In the Fourier transformation of the Ru K-edge *k*<sup>3</sup>-weighted EXAFS (extended X-ray absorption fine structure) spectrum of RuMn<sub>2</sub>/HT (Figure 1b) a peak near 3.5 Å, corresponding to the contiguous Ru sites (Ru–O–Ru),<sup>[11]</sup> was barely detected.

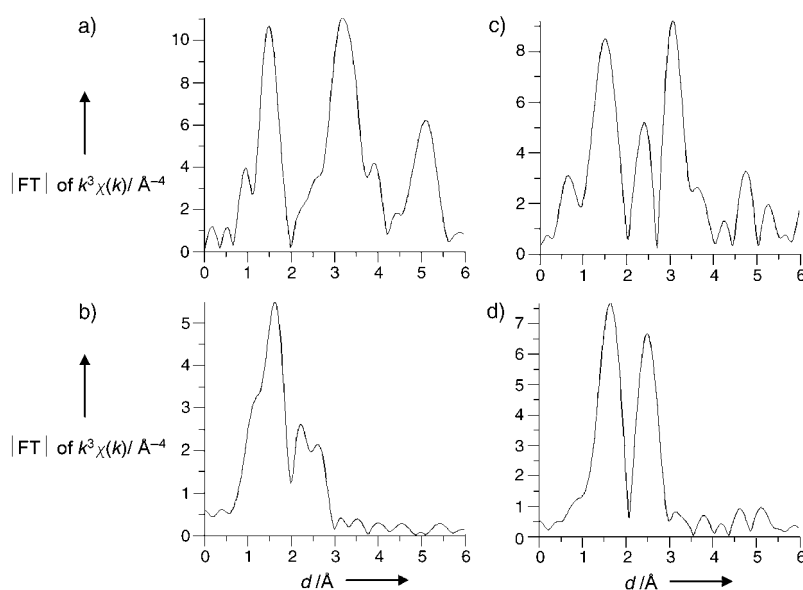

**Figure 1.** Fourier transformation (FT) of the *k*<sup>3</sup>-weighted K-edge EXAFS spectrum of a) RuO<sub>2</sub>, b) RuMn<sub>2</sub>/HT (Ru K-edge), c) β-MnO<sub>2</sub>, and d) RuMn<sub>2</sub>/HT (Mn K-edge). The phase shift was not corrected.

The coordination number (CN), distance (*R*), and Debye–Waller factor ( $\Delta\sigma$ ) of the Ru–O, Ru–Mg, and Ru–Mn bonds, as estimated by a curve-fitting analysis,<sup>[8]</sup> are listed in Table 1. The Ru<sup>IV</sup> species of RuMn<sub>2</sub>/HT are surrounded by six oxygen atoms with different bond distances. The shortest Ru–O bond was assigned to a Ru<sup>IV</sup>–OH moiety.<sup>[12]</sup> Two bonds of Ru–Mg and Ru–Mn shells, with CNs of 0.9 and 1.9, respectively, prove that the Ru<sup>IV</sup> species is in the vicinity of the Mg cation within the Brucite-like sheets and two Mn cations on the HT surface. Furthermore, a Mn–Mn shell with a distance of 2.32 Å and CN of 1.1 shows the formation of dimeric Mn<sup>IV</sup> cation species.<sup>[13]</sup>

The above results show a Ru<sup>IV</sup>Mn<sup>IV</sup>Mn<sup>IV</sup> trimetallic species on the HT surface, as shown in Figure 2, in which dimeric Mn–Mn species are connected to a single Ru<sup>IV</sup> cation through OH groups and water. To our knowledge, this is the first report of the preparation of heterotrimetallic species

[\*] Dr. K. Ebitani, K. Motokura, Dr. T. Mizugaki, Prof. Dr. K. Kaneda  
Graduate School of Engineering Science, Osaka University  
1–3 Machikaneyama, Toyonaka Osaka 560-8531 (Japan)  
Fax: (+81) 6-6850-6260  
E-mail: kaneda@cheng.es.osaka-u.ac.jp


[\*\*] This work was supported by a Grant-in-Aid for Scientific Research from the Ministry of Education, Culture, Sports, Science and Technology of Japan. We thank Prof. M. Nomura (KEK, PF) and Dr. T. Uruga (SPring-8) for XAFS measurements.

Supporting information for this article is available on the WWW under <http://www.angewandte.org> or from the author.

**Table 1:** Curve-fitting results for K-edge EXAFS of Ru and Mn.

Sample	Shell	CN <sup>[a]</sup>	R [Å] <sup>[b]</sup>	$\Delta\sigma$ [Å <sup>2</sup> ] <sup>[c]</sup>
RuMn <sub>2</sub> /HT	Ru-K			
	Ru-O(1)	2.1	1.97	-0.0079
	Ru-O(2)	2.1	2.07	-0.0045
	Ru-O(3)	1.1	1.83	-0.0088
	Ru-O(4)	0.6	2.61	-0.0087
	Ru-Mg	0.9	3.19	-0.1023
	Ru-Mn	1.9	3.28	0.0499
	Mn-K			
	Mn-O(1)	2.6	1.85	-0.0030
	Mn-O(2)	3.1	1.98	-0.0060
RuO <sub>2</sub> <sup>[d]</sup>	Mn-Mn	1.1	2.32	-0.0017
	Ru-O(1)	2	1.94	-
	Ru-O(2)	4	1.98	-
$\beta$ -MnO <sub>2</sub> <sup>[e]</sup>	Mn-O	6	1.89	-
	Mn-Mn(1)	2	2.87	-
	Mn-Mn(2)	8	3.42	-

[a] Coordination number. [b] Interatomic distance. [c]  $\Delta\sigma$  is the difference between the Debye-Waller factor of the sample and that of the reference sample. [d] Taken from the crystallographic data.<sup>[11]</sup> [e] Taken from the crystallographic data.<sup>[26]</sup>

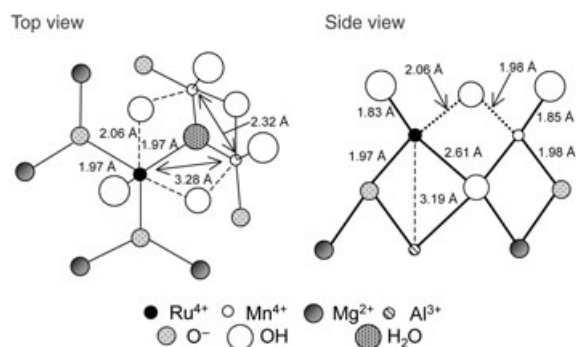

**Figure 2.** Proposed structure of the heterotrimetallic RuMnMn species on HT.

consisting of metal cations on a support involving metal oxide and metal hydroxides,<sup>[14]</sup> whereas the preparation of supported heterobimetallic or metal alloy species have been reported.<sup>[3]</sup> Adjusting the basicity of the hydroxy groups around the Ru<sup>IV</sup> cation, produced by reaction of the surface OH groups of HT with RuCl<sub>3</sub> species,<sup>[7d]</sup> brought about selective immobilization of Mn cations in the vicinity of the Ru species to give the unique Ru<sup>IV</sup>Mn<sup>IV</sup>Mn<sup>IV</sup> sites.

The catalytic ability of the RuMnMn species was explored in the oxidation of alcohol with O<sub>2</sub> at atmospheric pressure (Table 2).<sup>[15,16]</sup> The trimetallic RuMn<sub>2</sub>/HT shows a higher catalytic activity than Ru/HT,<sup>[7d]</sup> Ru/Al<sub>2</sub>O<sub>3</sub>,<sup>[15c,e]</sup> and RuO<sub>2</sub>,<sup>[15a]</sup> which are typical heterogeneous Ru catalysts for the oxidation of benzyl alcohol (1).<sup>[17]</sup> Benzyl alcohol was oxidized to benzal-

**Table 2:** Oxidation of benzyl alcohol (1) in the presence of various Ru catalysts under 1 atm O<sub>2</sub>.<sup>[a]</sup>

Entry	Catalyst	Conv. [%] <sup>[b]</sup>	Yield [%] <sup>[b]</sup>
1	RuMn <sub>2</sub> /HT	100	99
2	reuse 1 <sup>[c]</sup>	100	99
3	reuse 2 <sup>[c]</sup>	100	98
4	reuse 3 <sup>[c]</sup>	100	99
5	Ru/HT	66	66
6	Ru/Al <sub>2</sub> O <sub>3</sub> <sup>[d]</sup>	56	55
7	RuO <sub>2</sub> · <i>n</i> H <sub>2</sub> O	5	4
8	Mn <sub>2</sub> /HT <sup>[e]</sup>	0	0
9	HT	0	0

[a] Reaction conditions: catalyst (3 mol% Ru), benzyl alcohol (1 mmol), toluene (5 mL), 60°C, 1 atm O<sub>2</sub>, 1 h. [b] Conversions and yields were determined by GC analysis using an internal standard method based on benzyl alcohol. [c] Catalyst recovered and reused. [d] Prepared by the reported procedure.<sup>[15c]</sup> [e] 6 mol% Mn.

dehyde (2) quantitatively within 1 h in the presence of the RuMn<sub>2</sub>/HT catalyst.<sup>[18]</sup>

The initial turnover frequency based on Ru for RuMn<sub>2</sub>/HT (140 h<sup>-1</sup>) is almost five times larger than that for Ru/HT. On a 10-mmol scale oxidation of 1 in the presence of 0.1 mol% Ru, the turnover number based on Ru reached 840 at 90°C. Moreover, the high catalytic ability of RuMn<sub>2</sub>/HT was demonstrated by the quantitative oxidation of 1 within 10 h, even at 40°C.


As displayed in Table 3, the RuMn<sub>2</sub>/HT catalyst selectively oxidizes a wide variety of alcohols. Primary and secondary benzylic alcohols are converted into the corresponding carbonyl compounds in high yield (entries 1–3). The catalysis is also chemoselective; RuMn<sub>2</sub>/HT preferentially oxidizes primary over secondary hydroxy groups, as shown by the selective oxidation of 1-[(4'-hydroxymethyl)phenyl]ethanol to 1-[(4'-formyl)phenyl]ethanol in 98% yield (Scheme 1).

In the case of cyclopropyl(phenyl)methanol, the hydroxy group was oxidized without cleavage of the cyclopropyl ring

**Table 3:** Oxidation of various alcohols catalyzed by RuMn<sub>2</sub>/HT in the presence of O<sub>2</sub>.<sup>[a]</sup>

Entry	Alcohol	Product	<i>t</i> [h]	Conv. [%]	Yield [%] <sup>[b]</sup>
1	Benzyl alcohol (1)	Benzaldehyde (2)	1	100	99
2	1-Phenylethanol	Acetophenone	3.5	100	92
3	Benzhydrol	Benzophenone	2	94	93
4	Cyclopropyl(phenyl)methanol	Cyclopropyl phenyl ketone	6	100	99
5	Cinnamyl alcohol	Cinnamaldehyde	1.5	100	97
6	(2-Hydroxymethyl)thiophene	2-Thiophenecarboxaldehyde	2	100	89
7	2-Aminobenzyl alcohol	2-Aminobenzaldehyde	21	100	100

[a] Reaction conditions: catalyst (2 mol% Ru), alcohol (1 mmol), toluene (5 mL), 60°C, O<sub>2</sub> flow. [b] Yields were calculated based on alcohols.

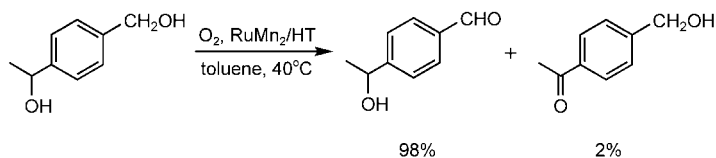

**Scheme 1.** Selective oxidation of primary hydroxy groups by RuMn<sub>2</sub>/HT catalyst.

(entry 4). Oxidation of cinnamyl alcohol proceeded smoothly without affecting the carbon–carbon double bond (entry 5). Furthermore, RuMn<sub>2</sub>/HT effectively catalyzes the oxidation of (2-hydroxymethyl)thiophene, a heteroaromatic alcohol, to 2-thiophenecarboxaldehyde, in high yield (entry 6), and the oxidation of 2-aminobenzyl alcohol to 2-aminobenzaldehyde, quantitatively (entry 7), in contrast to the homogeneous Pd and Ru complexes.<sup>[16]</sup>

The spent RuMn<sub>2</sub>/HT catalyst could be readily separated from the reaction mixture by filtration. The EXAFS spectrum of the recovered RuMn<sub>2</sub>/HT catalyst confirmed retention of the original RuMnMn structure, and ICP (inductively coupled plasma) analysis of the filtrate indicated no leaching of Ru and Mn species during the oxidation. The RuMn<sub>2</sub>/HT catalyst could be reused while maintaining the same high catalytic activity and selectivity (Table 2, entries 2–4). When the catalyst was removed at about 50% conversion of the alcohol, no further oxidation was detected in the filtrate after 3 h under 1 atm O<sub>2</sub> which shows that the present alcohol oxidations proceed at the interface between the catalyst surface and the liquid phase.


To the best of our knowledge, RuMn<sub>2</sub>/HT is the most effective, environmentally benign Ru catalyst for the oxidation of benzylic and aromatic allylic alcohols in the liquid phase<sup>[15,16c,d,19]</sup> with the advantages of 1) high catalytic activity, even with O<sub>2</sub> at 1 atm as the sole oxidant, 2) wide applicability to alcohols, including those containing heteroatoms, 3) simple preparation and work-up procedures, and 4) reusability as a solid catalyst.

The Mn cations in the RuMnMn species evidently play a pivotal role in improving the Ru-catalyzed alcohol oxidation since Mn<sub>2</sub>/HT does not catalyze the reaction (Table 2, entry 8). We have proposed a catalytic cycle for the alcohol oxidation (Scheme 2)<sup>[20]</sup> that proceeds via a ruthenium alkoxide intermediate, which undergoes β-hydrogen elimination to produce the carbonyl compound and a ruthenium hydride species, as observed by IR spectroscopy.<sup>[10]</sup> Reaction of this hydride with O<sub>2</sub> and subsequent ligand-exchange with the alcohol completes the catalytic cycle.<sup>[15b,e]</sup>

A rate equation based on a Michaelis–Menten-type model<sup>[21]</sup> for this proposed mechanism [Eq. (1)] agrees well with the kinetic data.



For the RuMn<sub>2</sub>/HT-catalyzed oxidation of **1**,  $K_M$  and  $k_2$  were calculated to be 2.96 mM and 0.047 s<sup>-1</sup>, respectively, at 60 °C. The rate constant ( $k_2$ ) of β-hydrogen elimination from the ruthenium alkoxide intermediate is therefore almost twice that for the Mn-free Ru/HT. The β-hydrogen elimination is considered as the rate-determining step in the overall alcohol oxidation from the primary kinetic isotope effect in the competitive oxidation of **1** and C<sub>6</sub>D<sub>5</sub>CD<sub>2</sub>OH (4.2).<sup>[15b,e]</sup> Thus, the Mn cations in the heterotrimetallic sites facilitate β-hydrogen elimination from the ruthenium alkoxide intermediate. Removing the water molecule that binds the Ru and Mn cations improves the situation of the Ru species during β-hydrogen elimination by, for example, producing a coordinately unsaturated Ru site.<sup>[16c]</sup>

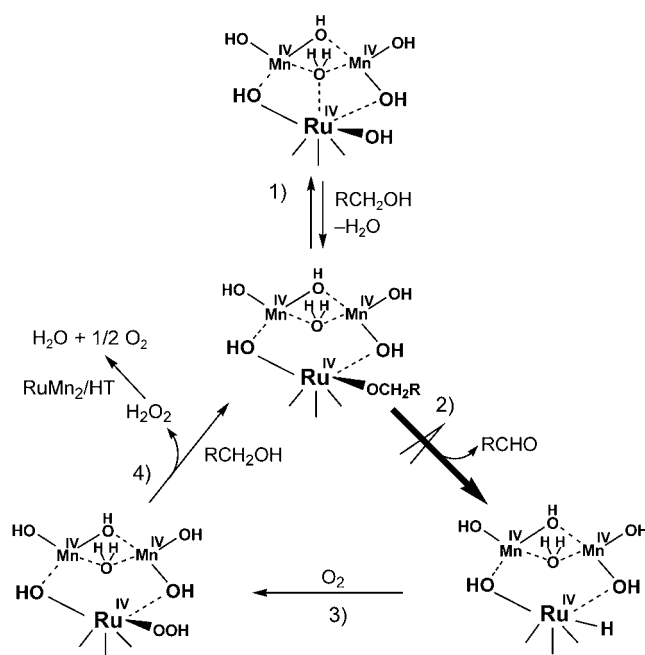

**Scheme 2.** A proposed mechanism for the oxidation of a primary alcohol by trimetallic RuMnMn sites.

For the secondary alcohol 1-phenylethanol,  $K_M$  and  $k_2$  were found to be 133 mM and 0.026 s<sup>-1</sup>, respectively, at 60 °C. Importantly, the  $K_M$  value is significantly greater than that for the oxidation of **1**, which is reflected in the preferential oxidation of primary hydroxy groups by this species.<sup>[22]</sup> The formation of metal alkoxide intermediates of primary alcohols is favored over secondary alcohols in the ligand-exchange step.<sup>[23]</sup>

In summary, a robust heterotrimetallic Ru<sup>IV</sup>Mn<sup>IV</sup>Mn<sup>IV</sup> species coordinated to a hydrotalcite surface as a macroligand facilitates the highly efficient aerobic oxidation of alcohols. Such cooperative action among high-valence metal cations in a heterometallic species on a solid surface provides a unique protocol for the preparation of functionalized heterogeneous catalysts for environmentally benign organic syntheses.<sup>[24]</sup> Ongoing efforts are focused on creating high-valence Ru cation species, that is, Ru<sup>VI</sup> and Ru<sup>VII</sup>, based on the redox interaction within a heterometallic site for highly efficient epoxidation and dihydroxylation reactions of alkenes with molecular oxygen.

## Experimental Section

Ru/HT<sup>[7d]</sup> was treated with an aqueous solution of MnCl<sub>2</sub>·4H<sub>2</sub>O to afford RuMn<sub>2</sub>/HT.<sup>[10]</sup> Elemental analysis (%) calcd for Ru<sub>0.071</sub>Mn<sub>0.142</sub>/Mg<sub>6</sub>Al<sub>2</sub>(OH)<sub>16</sub>CO<sub>3</sub>: Ru 1.03, Mn 1.12, Mg 21.0, Al, 8.14; found: Ru 1.05, Mn 1.20, Mg 21.4, Al 7.9.

The X-ray absorption spectra were recorded at the BL01B1 beamline in SPring-8 of JASRI, Japan (2003B0944-UXa-np and 2004A489-NXa-np) and at the BL-10B beamline of PF at KEK, Japan (2001G143 and 2002G102). The data were reduced using computer

systems at the Data Processing Center of Kyoto University according to a previously reported procedure.<sup>[25]</sup>

Received: November 13, 2004

Revised: December 29, 2004

Published online: April 28, 2005

**Keywords:** alcohols · heterogeneous catalysis · oxidation · ruthenium · supported catalysts

- [1] a) A. M. Argo, J. F. Odzak, F. S. Lai, B. C. Gates, *Nature* **2002**, *415*, 623; b) A. Suzuki, A. Yamaguchi, T. Chihara, Y. Inada, M. Yuasa, M. Abe, M. Nomura, Y. Iwasawa, *J. Phys. Chem. B* **2004**, *108*, 5609.
- [2] a) N. Wheatley, P. Kalck, *Chem. Rev.* **1999**, *99*, 3379; b) B. H. Holm, E. I. Solomon, *Chem. Rev.* **2004**, *104*, 347.
- [3] *Handbook of Heterogeneous Catalysis* (Eds.: G. Ertl, H. Knözinger, J. Weitkamp), VCH, Weinheim, **1997**.
- [4] S. J. Tauster, S. C. Fung, L. R. Garten, *J. Am. Chem. Soc.* **1978**, *100*, 170.
- [5] F. Cavani, F. Trifirò, A. Vaccari, *Catal. Today* **1991**, *11*, 173.
- [6] For typical catalysis of hydrotalcites as solid bases, see: B. M. Choudary, M. L. Kantam, B. Kavita, C. V. Reddy, K. K. Rao, F. Figueras, *Tetrahedron Lett.* **1998**, *39*, 3555; T. Honma, M. Nakajo, T. Mizugaki, K. Ebitani, K. Kaneda, *Tetrahedron Lett.* **2002**, *43*, 6229.
- [7] For typical heterogeneous metal catalysts based on HT, see: a) B. Sels, D. De Vos, M. Buntinx, F. Pierard, A. Kirsch-De Mesmaeker, P. A. Jacobs, *Nature* **1999**, *400*, 8565; b) T. Nishimura, N. Kakiuchi, M. Inoue, S. Uemura, *Chem. Commun.* **2000**, 1245; c) B. M. Choudary, N. S. Choudary, S. Madhi, M. L. Kantam, *Angew. Chem.* **2001**, *113*, 4755; *Angew. Chem. Int. Ed.* **2001**, *40*, 4619; d) K. Motokura, D. Nishimura, K. Mori, T. Mizugaki, K. Ebitani, K. Kaneda, *J. Am. Chem. Soc.* **2004**, *126*, 5662.
- [8] *X-ray Absorption: Principles, Applications, and Techniques of EXAFS, SEXAFS, and XANES* (Eds.: D. C. Königsberger, R. Prins), Wiley, New York, **1988**.
- [9] For a recent review on immobilization of metal species, see: C. Copéret, M. Chabanas, R. P. Saint-Arroman, J.-M. Basset, *Angew. Chem.* **2003**, *115*, 164; *Angew. Chem. Int. Ed.* **2003**, *42*, 156.
- [10] See Supporting Information.
- [11] P. Triggs, *Helv. Phys. Acta* **1985**, *58*, 657.
- [12] Two Ru–O bonds of 1.83 and 2.07 Å are assigned to Ru–OH and Ru–OH<sub>2</sub>, respectively. See: P. Dubourdeaux, M. Tavarès, A. Grand, R. Ramasseul, J.-C. Marchon, *Inorg. Chim. Acta* **1995**, *240*, 657; A. Liobet, D. J. Hodgson, T. Meyer, *Inorg. Chem.* **1990**, *29*, 3760.
- [13] The Mn–Mn distance is slightly shorter than that in bis-(hydroxo)-bridged Mn<sup>IV</sup> dimers (2.73–2.93 Å). See: M. J. Baldwin, T. L. Stemmler, P. J. Riggs-Gelasco, M. L. Kirk, J. E. Penner-Hahn, V. L. Pecoraro, *J. Am. Chem. Soc.* **1994**, *116*, 11349.
- [14] Generation of heterometallic species has not been reported on HT containing Pd, Os, or W.<sup>[7c]</sup>
- [15] For selected heterogeneous Ru catalysts for alcohol oxidation, see: a) M. Matsumoto, M. Watanabe, *J. Org. Chem.* **1984**, *49*, 3435; b) K. Yamaguchi, K. Mori, T. Mizugaki, K. Ebitani, K. Kaneda, *J. Am. Chem. Soc.* **2000**, *122*, 7144; c) K. Yamaguchi, N. Mizuno, *Angew. Chem.* **2002**, *114*, 4720; *Angew. Chem. Int. Ed.* **2002**, *41*, 4538; d) M. Musawir, P. N. Davey, G. Kelly, I. V. Kozhevnikov, *Chem. Commun.* **2003**, 1414; e) K. Yamaguchi, N. Mizuno, *Chem. Eur. J.* **2003**, *9*, 4353. See also T. Mallat, A. Baiker, *Chem. Rev.* **2004**, *104*, 3037 as a recent review.
- [16] For representative aerobic alcohol oxidations by homogeneous metal complexes, see: a) A. Hanyu, E. Takezawa, S. Sakaguchi, Y. Ishii, *Tetrahedron Lett.* **1998**, *39*, 5557; b) G.-J. ten Blink, I. W. C. E. Arends, R. A. Sheldon, *Science* **2000**, *287*, 1636; c) P. A. Shapley, N. Zhang, J. L. Allen, D. H. Pool, H.-C. Liang, *J. Am. Chem. Soc.* **2000**, *122*, 1079; d) A. Dijkman, A. Marino-González, A. Mairata i Payeras, I. W. C. E. Arends, R. A. Sheldon, *J. Am. Chem. Soc.* **2001**, *123*, 6826.
- [17] See the Supporting Information for typical time courses for the oxidation of **1**.
- [18] A control experiment was performed using benzaldehyde in the presence of RuMn<sub>2</sub>/HT and water at 60 °C in toluene under oxygen. Benzaldehyde was quantitatively recovered showing that it is not oxidized further under these conditions. See Supporting Information.
- [19] RuMn<sub>2</sub>/HT is highly effective for the oxidation of benzylic and aromatic allylic alcohols, but not for primary aliphatic alcohols; the oxidation of 1-octanol with RuMn<sub>2</sub>/HT (2 mol-% Ru) afforded octanal in 62% yield at 60 °C after 5 h. A CoCeRu trimetallic catalyst shows a high activity for the aerobic oxidation of primary aliphatic alcohols: H.-B. Ji, T. Mizugaki, K. Ebitani, K. Kaneda, *Tetrahedron Lett.* **2002**, *43*, 7179; K. Ebitani, H.-B. Ji, T. Mizugaki, K. Kaneda, *J. Mol. Catal. A* **2004**, *212*, 161.
- [20] 1) The addition of a radical scavenger (2,6-di-*tert*-butyl-*p*-cresol) did not affect the rate of the oxidation. 2) Treatment of RuMn<sub>2</sub>/HT with **1** under argon afforded an IR signal of a Ru–H species at 2120 cm<sup>-1</sup>.<sup>[10,16d]</sup> This species disappeared upon exposure to O<sub>2</sub>. 3) During the oxidation of **1**, the ratio of O<sub>2</sub> consumed to **2** was 1:2.
- [21] R. W. Missen, C. A. Mims, B. A. Saville, *Introduction to Chemical Reaction Engineering and Kinetics*, Wiley, New York, **1999**. The initial rate of oxidation of **1** is proportional to the amount of RuMn<sub>2</sub>/HT and independent of the oxygen pressure.
- [22] If the second step in Equation (1) is the rate-determining step, the K<sub>M</sub> value can be regarded as a dissociation equilibrium constant ( $k_{-1}/k_1$ ) of the first step. See ref. [21].
- [23] A similarly high chemoselectivity for primary alcohols has been observed in the Zr(OAc)<sub>2</sub>-catalyzed oxidation of alcohols: K. Kaneda, Y. Kawanishi, S. Teranishi, *Chem. Lett.* **1984**, 1481.
- [24] P. T. Anastas, J. C. Warner, *Green Chemistry: Theory and Practice*, Oxford University Press, Oxford, **1998**.
- [25] T. Yamamoto, T. Tanaka, S. Takenaka, S. Yoshida, T. Onari, Y. Takahashi, T. Kosaka, S. Hasegawa, M. Kudo, *J. Phys. Chem. B* **1999**, *103*, 2385.
- [26] H. W. Baur, *Acta Crystallogr., Sect. B* **1976**, *32*, 220.